



A New Technique for Wirebonding Using Indium Spheres

by Kimberley A. Olver

ARL-TR-5240

July 2010

NOTICES

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

Army Research Laboratory

Adelphi, MD 20783-1197

ARL-TR-5240**July 2010**

A New Technique for Wirebonding Using Indium Spheres

Kimberley A. Olver

Sensors and Electron Devices Directorate, ARL

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188		
<p>Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</p> <p>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</p>					
1. REPORT DATE (DD-MM-YYYY) July 2010		2. REPORT TYPE Final		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE A New Technique for Wirebonding Using Indium Spheres			5a. CONTRACT NUMBER		
			5b. GRANT NUMBER		
			5c. PROGRAM ELEMENT NUMBER		
6. AUTHOR(S) Kimberley A. Olver			5d. PROJECT NUMBER		
			5e. TASK NUMBER		
			5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: RDRL-SEE-I 2800 Powder Mill Road Adelphi, MD 20783-1197			8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TR-5240		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)			10. SPONSOR/MONITOR'S ACRONYM(S)		
			11. SPONSOR/MONITOR'S REPORT NUMBER(S)		
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited.					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT <p>A new technique has been developed for wirebonding mercury cadmium telluride (MCT) devices using indium spheres. Indium powder with a mesh size of 170/200 is made up of indium spheres. These spheres are used as solder between the gold pad on the MCT device and the gold ball of the wirebond. This novel technique eliminates damage that typically occurs to the MCT material under gold wirebonding pads due to force and ultrasonic power needed in wirebonding.</p>					
15. SUBJECT TERMS Wirebonding indium, Mercury Cadmium Telluride, MCT					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UU	18. NUMBER OF PAGES 14	19a. NAME OF RESPONSIBLE PERSON Kimberley A. Olver
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code) (301) 394-2048

Contents

List of Figures	iv
Acknowledgments	v
1. Introduction	1
2. Procedure and Results	2
4. Conclusion	4
5. References	5
Distribution List	6

List of Figures

Figure 1. Indium spheres placed on the device package.....	1
Figure 2. A scanning electron microscope (SEM) image of indium spheres.	1
Figure 3. Indium balls placed on the package in close proximity to the devices being wirebonded.....	2
Figure 4. Indium ball statically held onto the gold ball at the end of the capillary.	3
Figure 5. Capillary brought over to the device bonding area.	3
Figure 6. Indium makes contact with the device pad and the first bond is completed.	3
Figure 7. Capillary is brought over to the package bonding pad and the second bond is completed.....	4
Figure 8. Completed indium sphere wirebonds on an MCT device.	4

Acknowledgments

The author would like to thank Dr. Wendy Sarney of the Electro-optic (EO) Materials and Devices branch for helping with the scanning electron microscope (SEM) image of the indium spheres.

INTENTIONALLY LEFT BLANK.

1. Introduction

A novel technique for gold wirebonding of delicate mercury cadmium telluride (MCT) devices has been developed. Gold ball wirebonding to MCT devices is challenging. The act of applying force and ultrasonic power to MCT very easily creates damage under the device bond pads, damage that sometimes goes unnoticed until testing the device's integrity at a later date. Indium spheres placed between the gold wirebond ball and the gold bonding pad on the MCT material allows one to use less force and ultrasonic power to attach the wire and acts as a soft solder in the process. In this study, an indium powder of a mesh size of 170/200 is used as a cushion between the free air gold ball and the device pad being wirebonded. Indium powder is made up of small (70–90 microns diameter) indium spheres (figures 1 and 2). The properties of indium make it a good choice in this technique. Indium is malleable and thermally and electrically conductive, and has a low oxide formation level. These qualities make it an ideal cold-welding material.

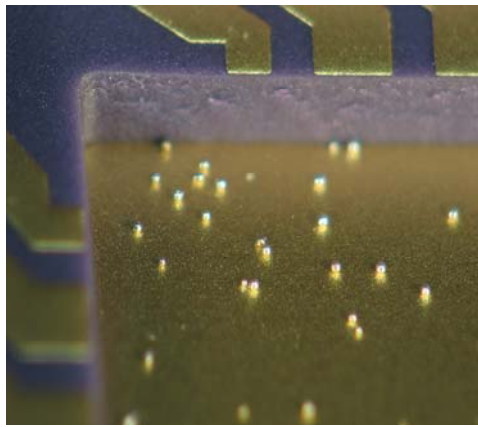


Figure 1. Indium spheres placed on the device package.

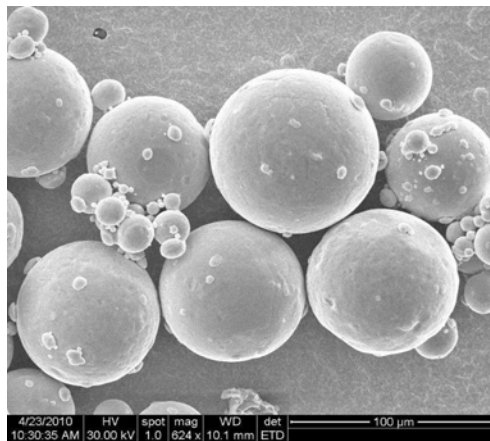


Figure 2. A scanning electron microscope (SEM) image of indium spheres.

2. Procedure and Results

For this technique, the equipment used was a Marpet Enterprise, Inc. (MEI), 1204B Hybrid Ball Wirebonder (1) threaded with Kulicke & Soffa AW14 0.7-mil gold wire. The ceramic capillary tool make and size was a Gaiser Tool Company #1513-12-375 GM-20D (2). The indium spheres were purchased from Indium Corporation of America and the mesh size of the indium (powder) was 170/200 (3).

Conventional ultrasonic ball wirebonding (4) consists of several steps: welding the wire to the contact pad on the device (known as the first bond); forming the wire loop as the capillary is moved to the second bond position; creating the second bond (also called the crescent or stitch bond), which connects the wire to the device package; and firing the electric flame off (EFO), which forms the next ball at the bottom of the capillary tool. This new technique follows the traditional steps of ball wirebonding with the addition of placing an indium sphere in between the gold wirebond ball and the device bond pad on the first bond.

Indium spheres were placed onto the package such that they were in close proximity to the devices being bonded (figure 3). The ultrasonic power and the firing time on the transducer unit of the wirebonder were turned to near zero for the first bond. Normal settings for power and time (based on the individual wire bonder equipment) were used for the second bond. At the first bond position the capillary is brought over to an indium sphere, the capillary is lowered just to the point that the gold ball on the end of the capillary makes contact with the indium (figure 4). Pressure is not applied to the indium; instead, static electricity holds the indium sphere to the gold ball. The capillary is then brought up slightly and the indium ball is positioned directly over the pad that will be accepting the first bond (figure 5). The capillary is brought down to the bond pad and slight pressure is applied. The indium flattens, adhering to the metal bond pad, and the gold ball adheres to the indium on the pad (figure 6). The capillary then rises to the loop height position, and the wire is brought over to the second bond position. The second bond is formed, the wire disconnects, the EFO fires, and the cycle is complete (figure 7). Figure 8 shows the completed wirebonds. When the indium sphere wirebonding has been completed, the unused indium spheres are simply put back into the container by a gentle tapping on the back of the package over the container.

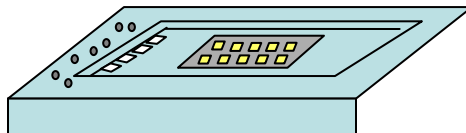


Figure 3. Indium balls placed on the package in close proximity to the devices being wirebonded.

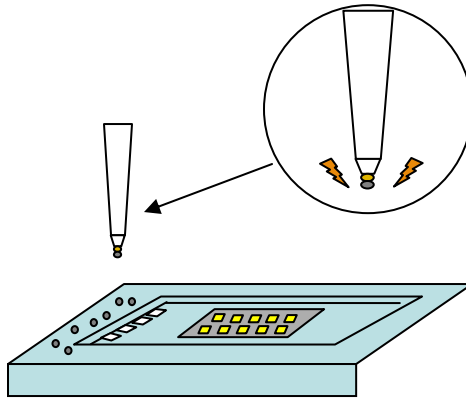


Figure 4. Indium ball statically held onto the gold ball at the end of the capillary.

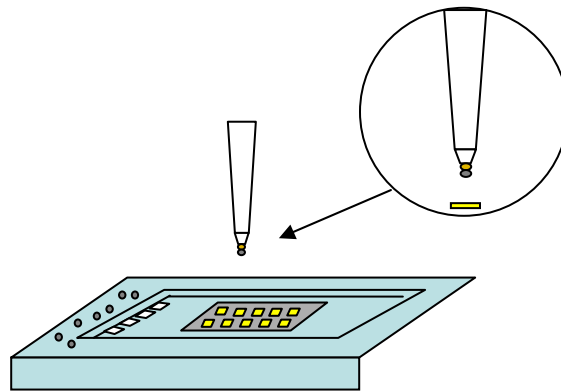


Figure 5. Capillary brought over to the device bonding area.

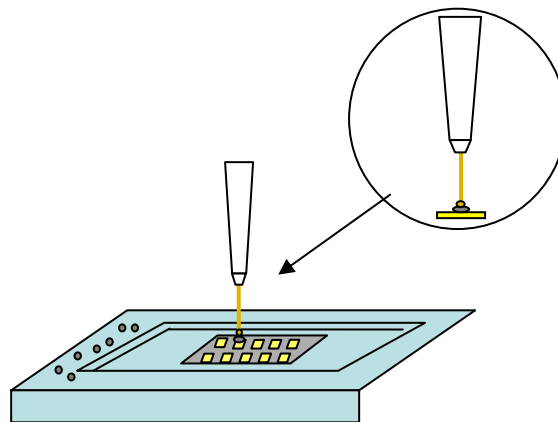


Figure 6. Indium makes contact with the device pad and the first bond is completed.

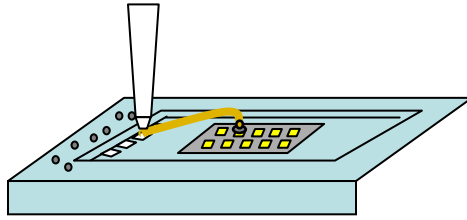


Figure 7. Capillary is brought over to the package bonding pad and the second bond is completed.

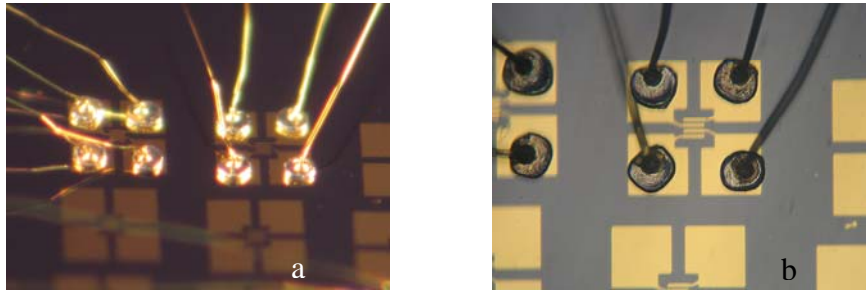


Figure 8. Completed indium sphere wirebonds on an MCT device.

4. Conclusion

This new technique of wirebonding works very well for wirebonding the delicate MCT material devices. It reduces or eliminates the damage caused by traditional wirebonding processes by allowing one to perform wirebonding without using the ultrasonic power and force that damages the device material. This method has also been used successfully for wirebonding devices when there has been an issue with metallization liftoff of the bond pads.

There is one limitation to this technique, This technique is not suitable for wirebonding devices that will experience an operating temperature of 157 °C or higher—the melting temperature of indium.

5. References

1. *MEI 1204B Hybrid Ball Bonder Operations Manual*, Marpet Enterprises, Inc., Danvers, MA 01923.
2. Gaiser Tool Company Semiconductor and Hybrid Microelectronics Wirebonding Tools Catalog, Gaiser Tool Company, Ventura, CA 93003. www.gaisertool.com (accessed March, 2010).
3. Indium Corporation of America, Utica, NY 13502. www.indium.com (accessed March 2010).
4. Harman, G. *Wirebonding in Microelectronics Materials, Processes, Reliability, and Yield*, 2nd ed., McGraw-Hill, 1997.

NO. OF
COPIES ORGANIZATION

1 ELEC ADMNSTR
DEFNS TECHL INFO CTR
ATTN DTIC OCP
8725 JOHN J KINGMAN RD STE 0944
FT BELVOIR VA 22060-6218

1 CD OFC OF THE SECY OF DEFNS
ATTN ODDRE (R&AT)
THE PENTAGON
WASHINGTON DC 20301-3080

1 US ARMY RSRCH DEV AND ENGRG
CMND
ARMAMENT RSRCH DEV & ENGRG
CTR
ARMAMENT ENGRG & TECHN LGY
CTR
ATTN AMSRD AAR AEF T J MATTS
BLDG 305
ABERDEEN PROVING GROUND MD
21005-5001

1 PM TMS, PROFILER (MMS-P)
AN/TMQ-52
ATTN B GRIFFIES
BUILDING 563
FT MONMOUTH NJ 07703

1 US ARMY INFO SYS ENGRG CMND
ATTN AMSEL IE TD A RIVERA
FT HUACHUCA AZ 85613-5300

1 COMMANDER
US ARMY RDECOM
ATTN AMSRD AMR
W C MCCORKLE
5400 FOWLER RD
REDSTONE ARSENAL AL 35898-5000

1 US GOVERNMENT PRINT OFF
DEPOSITORY RECEIVING SECTION
ATTN MAIL STOP IDAD J TATE
732 NORTH CAPITOL ST NW
WASHINGTON DC 20402

1 US ARMY RSRCH LAB
ATTN RDRL CIM G T LANDFRIED
BLDG 4600
ABERDEEN PROVING GROUND MD
21005-5066

NO. OF
COPIES ORGANIZATION

11 US ARMY RSRCH LAB
ATTN IMNE ALC HRR
MAIL & RECORDS MGMT
ATTN RDRL CIM L TECHL LIB
ATTN RDRL CIM P TECHL PUB
ATTN RDRL SEE G WOOD
ATTN RDRL SEE I D BEEKMAN
ATTN RDRL SEE I J LITTLE
ATTN RDRL SEE I K OLVER
ATTN RDRL SEE I P UPPAL
ATTN RDRL SEE I
P WIJEWARNASURIYA
ATTN RDRL SEE I W SARNEY
ATTN RDRL SEE P GILLESPIE
ADELPHI MD 20783-1197

TOTAL: 19 (1 ELEC, 1 CD, 17 HCS)